



Quality	X39CrMo17-1		Martensitic Stainless Steel		Technical card 2018	
Number	1.4122				Lucefin Group	

Chemical composition

C%	Si% max	Mn% max	P% max	S% a) max	Cr%	Mo%	Ni% max	
0,33-0,45	1,00	1,50	0,040	0,030	15,5-17,5	0,80-1,30	1,00	EN 10088-3: 2014
± 0,02	+ 0,05	+ 0,04	+ 0,005	± 0,005	± 0,2	± 0,05	+ 0,03	

Product deviations are allowed

a) for improving machinability, it is allowed a controlled sulphur content of 0,015 % - 0,030 %; for polishability, it is suggested a controlled sulphur content of max 0,015 %

Temperature °C

Melting range	Hot-forming	Recrystallization +RA	Soft annealing +A	MMA welding – AWS electrodes pre-heating annealing after w. Difficult; address qualified electrodes producers
1480-1465	1100-930	not suitable	850-750 air	joint with steel carbon CrMo alloyed stainless
Isothermal annealing +I	Quenching +Q	Tempering +T		E309 E309 E309 – E308 cosmetic welding E309
not suitable	1060-980 air / oil / polymer (HRC 48)	750-650 air		

Transformation temperature during heating **Ac1 ~ 810, Ac3 ~ 900** and during cooling **Ms ~ 280, Mf ~ 130****Chemical treatment - Pickling** (15 - 25% HNO₃) + (1 - 8% HF) hot or cold**Mechanical properties**

Heat-treated material EN 10088-3: 2014 in conditions 1C, 1E, 1D, 1X, 1G, 2D

size	Testing at room temperature					a) for information only
mm	R	Rp 0.2	A%	Kv ₂ +20 °C	HBW a)	
from to	N/mm ²	N/mm ² min	min (L)	J min (L)	max	
	900 max	-	-	-	280	+A annealed material
60	750-950	550	12	15	-	+QT750 quenched and tempered
60	160	750-950	550	12	10	+QT750 quenched and tempered

Bright bars of heat-treated material EN 10088-3: 2014 in conditions 2H, 2B, 2G, 2P

size	Testing at room temperature						
mm	R	HBW a)		R	Rp 0.2	A%	Kv ₂ +20 °C
from to	N/mm ²	max	max	N/mm ²	N/mm ² min	min (L)	J min (L)
10 b)	1000	340		800-1050	650	8	-
10	16	1000	340	800-1050	600	8	-
16	40	980	310	750-1000	550	10	14
40	63	930	290	750-950	550	12	14
63	100	900	280	750-950	550	12	10
	+A annealed material					+QT750 quenched and tempered	

a) for information only

b) in the range of 1 mm ≤ d < 5 mm, values are valid only for rounds – the mechanical properties of non round bars of < 5 mm of thickness have to be agreed at the time of request and order

Forged

size	Testing at room temperature					
mm	R	Rp 0.2	A%	Kv +20 °C	HB a)	
from to	N/mm ²	N/mm ² min	min	J min	max	
	-	-	-	-	280	+A annealed material

a) for information only

Table of tempering values at room temperature on rounds of Ø 20 mm after quenching at 1050°C in oil

HB	455	432	432	432	442	442	421	400	319
HRC	48	46	46	46	47	47	45	43	34
Tempering °C	200	250	300	350	400	450	500	550	600

Minimum values at high temperatures on +QT750 material EN 10088-3: 2014

Rp 0.2 N/mm ²	540	535	530	520	510	490	470	
Test at °C	100	150	200	250	300	350	400	

Thermal expansion	$10^{-6} \cdot K^{-1}$	►	10.4	10.8	11.2	11.6
Modulus of elasticity	longitudinal GPa	215	212	205	200	190
Poisson number	ν	0,27-0,30 ~				
Electrical resistivity	$\Omega \cdot mm^2/m$	0.80				
Electrical conductivity	Siemens $\cdot m/mm^2$	1.25				
Specific heat	J/(Kg $\cdot K$)	430				
Density	Kg/dm 3	7.70				
Thermal conductivity	W/(m $\cdot K$)	15				
Relative magnetic permeability	μ_r	700-1000 ~				
°C		20	100	200	300	400


The symbol ► indicates temperature between 20 °C and 100 °C, 20 °C and 200 °C

Corrosion resistance	Atmospheric	Chemical	x organic and nitric acids
Fresh water	industrial marine	medium oxidizing reducing	
x			

Magnetic	yes
Machinability	low
Hardening	by quenching
Service temperature in air	good resistance to oxidation and heat up to 500 °C

Europe EN	USA UNS	USA ASTM	China GB	Russia GOST	Japan JIS	India IS	Republic of Korea KS
X39CrMo17-1				40Ch16M			

Tempering diagram

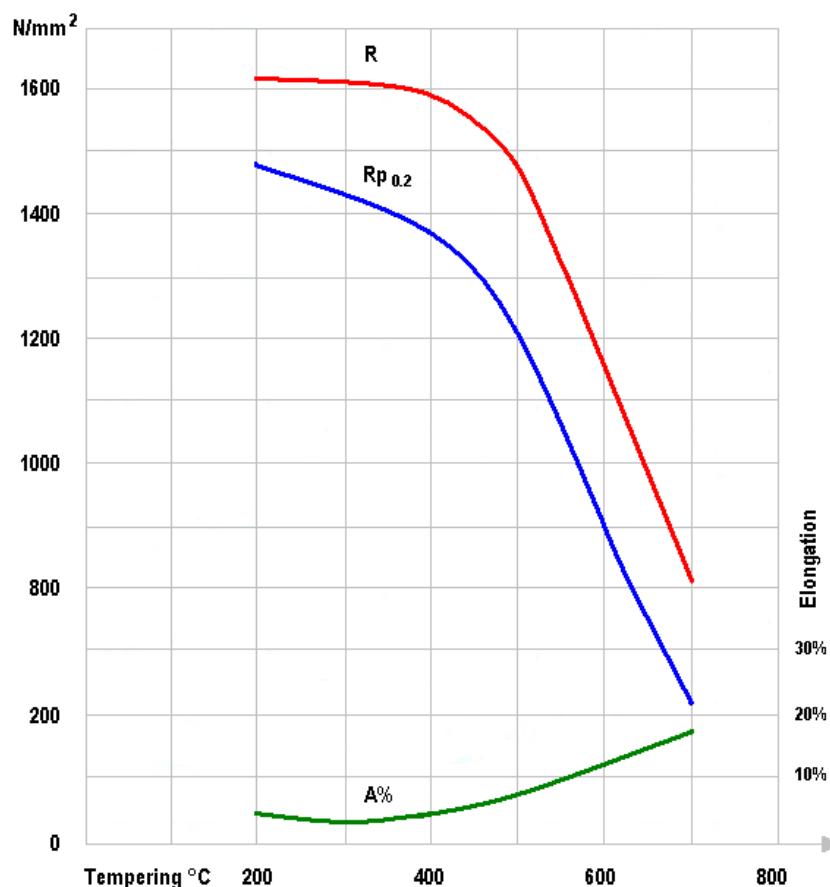

Mechanical testing on rounds of Ø 20 mm after quenching at 1050°C in oil